

WEST VIRGINIA DEPARTMENT OF TRANSPORTATION
DIVISION OF HIGHWAYS
MATERIALS CONTROL, SOILS AND TESTING DIVISION
MATERIALS PROCEDURE

QUALITY ASSURANCE OF REINFORCED CONCRETE CULVERT,
STORM DRAIN, AND SEWER PIPE

- 1.0 PURPOSE
- 1.1 To set forth the procedures which govern the Quality Assurance of reinforced concrete culvert, storm drain, and sewer pipe.
- 1.2 To set forth manufacturers Quality Control requirements.
- 1.3 To set forth acceptance inspection procedures.
- 1.4 To set forth documentation and shipping procedures.
- 2.0 SCOPE
- 2.1 This procedure will apply to all manufacturers of reinforced concrete culvert, storm pipe, and sewer pipe for use in West Virginia projects.
- 2.2 This procedure will establish the basis for acceptance of reinforced concrete pipe having a wall thickness of 115 mm or less.
- 2.3 This procedure will establish the basis for acceptance of reinforced concrete pipe having a wall thickness greater than 115 mm.
- 3.0 APPLICABLE SPECIFICATIONS
- 3.1 All standard types of reinforced concrete pipe are to be manufactured and tested in accordance with Section 714.2 of the Standard Specifications for Roads and Bridges.
- 3.2 Reinforced concrete pipe having a wall thickness of 115 mm or less, which is manufactured in accordance with the applicable specifications, is treated in the following manner to determine acceptability.

- 3.2.1 The three edge bearing test (AASHTO T-280) shall be used to determine the force required to produce the 0.25 mm crack and the minimum specified ultimate load.
- 3.2.2 The absorption test (AASHTO T-280) shall be conducted on samples selected from the wall of the pipe.
- 3.2.3 A plant inspection of the finished product is conducted to determine dimensional conformance and freedom from defects.
- 3.3 Reinforced concrete pipe having a wall thickness greater than 115 mm, which is manufactured in accordance with the applicable specifications, is treated in the following manner to determine acceptability.
 - 3.3.1 The compressive strength of the concrete will be determined by testing cores taken from the wall of the pipe. The manufacturer may choose to test this pipe as specified in Article 3.2.1, in which event the requirements for the 0.25 mm crack and the minimum specified ultimate load shall be met. This choice shall not be applied to a LOT (refer to Table 1) of pipe which has been previously cored and found unacceptable.
 - 3.3.2 The absorption test (AASHTO T-280) shall be conducted on samples selected from the wall of the pipe.
 - 3.3.3 A plant inspection of the finished product will be conducted by the Division to determine dimensional conformance, and freedom from defects.
- 4.0 QUALITY CONTROL REQUIREMENTS
 - 4.1 Quality Control is the responsibility of the manufacturer and shall include the following:
 - 4.1.1 Insure all component materials used in the fabrication of the pipe have been sampled, tested, and approved (Table 2).
 - 4.1.2 Insure quality workmanship as well as a quality product throughout the production.

- 4.1.3 To scribe into each piece of pipe the following:
- (a) Cast Date
 - (b) Class and Wall Type
 - (c) Manufacturer's Trademark
- 4.1.4 Notify the Division's representative upon the completion of casting of a LOT (Refer to Table 1) of pipe so the Division may select a representative sample and witness the testing.
- 4.1.5 To conduct the three edge bearing test or to secure cores to insure strength requirements are met (Section 3.2 and 3.3).
- 4.1.6 To conduct the absorption test (AASHTO T-280) on samples selected from the wall of the pipe.
- 4.1.7 Any LOT of pipe or portion of a LOT of pipe failing to meet the specification requirements will be stored separately from acceptable pipe.
- 4.1.8 Accurate inventory records containing the information required in Section 6.1.2 will be kept and maintained by the manufacturer.
- 5.0 ACCEPTANCE CRITERIA
- The Division will:
- 5.1 Sample and test the component materials to be used in the manufacturer of the reinforced concrete pipe at a frequency no less than the minimum frequency specified in Table 2.
- 5.2 Select representative samples of the LOT to be tested and:
- (a) Witness the three edge bearing test and/or the coring procedure
 - (b) Verify dimensional conformity
 - (c) Verify actual steel placement
 - (d) Determine the steel area
- 5.3 Insure each piece comprising the LOT is scribed as stated in 4.1.3.

5.4 Make a visual inspection of the LOT and designate unacceptable units to be removed or set apart from the approved pipe in the LOT.

6.0 SHIPPING REQUIREMENTS

6.1 The approved LOT of pipe or portion of the LOT can be shipped by the manufacturer providing the following provisions have been met:

6.1.1 The manufacturer will notify the Division's representative prior to each shipment so that the Division may maintain a current inventory with the manufacturing plant.

6.1.2 The manufacturer will supply one copy of the shipping invoice to Materials Control, Soils and Testing Division and one copy to the Division's representative at the project site. The invoice shall contain the following information.

- (a) Cast date of the approved LOT
- (b) Master laboratory number
- (c) Size, class, and wall type
- (d) Project number
- (e) Number of pieces

7.0 ACCEPTANCE PRACTICE


7.1 Insure the information on the shipping invoice, as required in Section 6.1.2, agrees with the shipment it accompanies. (Number of pieces, class, size, and type, and etc.).

7.2 Check each piece of pipe for the proper identification markings (Section 5.3) and make a visual inspection of each piece to insure there is no evidence of damage during shipment.

MP 711.03.30
ORIGINAL ISSUANCE: FEBRUARY 1963
1ST REVISION: MARCH 1993
2ND REVISION: NOVEMBER 1993
REISSUED: JANUARY 1995
PAGE 5 OF 5

8.0 COVERAGE REQUEST FROM PROJECT SITE

8.1 Request for coverage shall include the information as referenced on the shipping invoice, Section 6.1.2 and submitted on Form T-702.

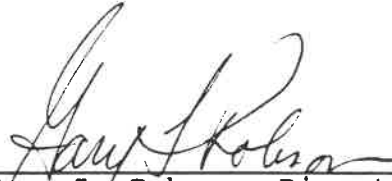

Gary L. Robson, Director
Materials Control, Soils
and Testing Division

GLR:d

Attachments

MP 711.03.30
ORIGINAL ISSUANCE: FEBRUARY 1963
1ST REVISION: MARCH 1993
2ND REVISION: NOVEMBER 1993
REISSUED: JANUARY 1995
ATTACHMENT 1
PAGE 1 OF 1

TABLE 1

SAMPLING AND TESTING FREQUENCY FOR REINFORCED CONCRETE PIPE

A production "LOT" is defined as follows:

It is pipe of the same size and class that is manufactured using the same process and similar materials. The production LOT shall not exceed the specified value of 1% of the LOT and the minimum number tested per LOT is as follows:

Number of Pipe Sections in the LOT	Number of Pipe Section to be Tested
0 to 300	1
301 to 800	2
801 to 1500	3
over 1500	3 plus 1 section per each 600 pieces or fraction thereof over 1500 pc. LOT

When the tests indicate that a production LOT is acceptable for State use, the LOT should be inspected by the Division's representative.

TABLE 2

<u>Construction Sampling</u>	<u>Sample Size</u>	<u>Minimum Frequency of Sampling and Testing (Note 1)</u>
Cement	4 kg	Semi-annually
Fine Aggregate	10 kg	Semi-annually
Coarse Aggregate	25 kg	Semi-annually
Water	1 L	Semi-annually
Reinforcing Steel	1/2 m for bars	Semi-annually
	1 m by the standard width for welded wire fabric	

Note 1: Construction materials supplied from a Division approved source, materials pretested at the source in a manner set forth in MP 700.00.10 (Sampling and Testing of Materials at the source) or other established procedures, may be used without sampling or testing at the manufacturing plant.

